


NASA/TM-2002-211649

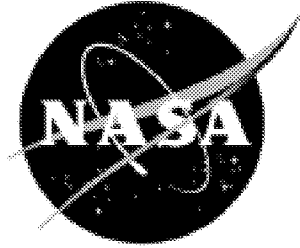

On the Thermal Model of Transverse Flow of Unidirectional Materials

Hsiang Tai
Langley Research Center, Hampton, Virginia

May 2002

The NASA STI Program Office . . . in Profile

Since its founding, NASA has been dedicated to the advancement of aeronautics and space science. The NASA Scientific and Technical Information (STI) Program Office plays a key part in helping NASA maintain this important role.

The NASA STI Program Office is operated by Langley Research Center, the lead center for NASA's scientific and technical information. The NASA STI Program Office provides access to the NASA STI Database, the largest collection of aeronautical and space science STI in the world. The Program Office is also NASA's institutional mechanism for disseminating the results of its research and development activities. These results are published by NASA in the NASA STI Report Series, which includes the following report types:

- **TECHNICAL PUBLICATION.** Reports of completed research or a major significant phase of research that present the results of NASA programs and include extensive data or theoretical analysis. Includes compilations of significant scientific and technical data and information deemed to be of continuing reference value. NASA counterpart of peer-reviewed formal professional papers, but having less stringent limitations on manuscript length and extent of graphic presentations.
- **TECHNICAL MEMORANDUM.** Scientific and technical findings that are preliminary or of specialized interest, e.g., quick release reports, working papers, and bibliographies that contain minimal annotation. Does not contain extensive analysis.
- **CONTRACTOR REPORT.** Scientific and technical findings by NASA-sponsored contractors and grantees.

- **CONFERENCE PUBLICATION.** Collected papers from scientific and technical conferences, symposia, seminars, or other meetings sponsored or co-sponsored by NASA.
- **SPECIAL PUBLICATION.** Scientific, technical, or historical information from NASA programs, projects, and missions, often concerned with subjects having substantial public interest.


TECHNICAL TRANSLATION. English-language translations of foreign scientific and technical material pertinent to NASA's mission.

Specialized services that complement the STI Program Office's diverse offerings include creating custom thesauri, building customized databases, organizing and publishing research results . . . even providing videos.

For more information about the NASA STI Program Office, see the following:

- Access the NASA STI Program Home Page at <http://www.sti.nasa.gov>
- Email your question via the Internet to help@sti.nasa.gov
- Fax your question to the NASA STI Help Desk at (301) 621-0134
- Telephone the NASA STI Help Desk at (301) 621-0390
- Write to:
NASA STI Help Desk
NASA Center for AeroSpace Information
7121 Standard Drive
Hanover, MD 21076-1320

NASA/TM-2002-211649

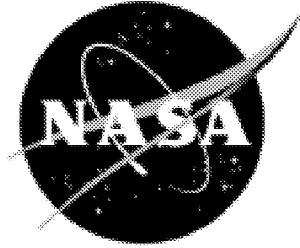

On the Thermal Model of Transverse Flow of Unidirectional Materials

Hsiang Tai

Langley Research Center, Hampton, Virginia

National Aeronautics and
Space Administration

Langley Research Center
Hampton, Virginia 23681-2199

May 2002

Available from:

NASA Center for AeroSpace Information (CASI)
7121 Standard Drive
Hanover, MD 21076-1320
(301) 621-0390

National Technical Information Service (NTIS)
5285 Port Royal Road
Springfield, VA 22161-2171
(703) 605-6000

Abstract

The thermal model for transverse heat flow of having single filament in a unit cell is extended. In this model, we proposed that two circular filaments in a unit cell of square packing array and obtained the transverse thermal conductivity of an unidirectional material.

I. Thermal Model

Predicting equivalent thermal conductivity of transverse flow in unidirectional composite materials is of interest in composite research. An expression for thermal conductivity can be obtained based on physical principle, either from the point of view of equivalent thermal flux or from equivalent temperature field. By considering the fibers as square slabs or circular cylinders embedded in the matrix, the simple rule of mixture can be applied to obtain the equivalent thermal conductivity. In 1967, Springer and Tsai [1] proposed a thermal model for transverse flow that is a compound model including both serial flow and parallel flow to account for the fiber shape geometry. The thermal model developed has a single circular filament located in the center of a square packing array. The resulting expression is in good agreement with experimental work. Recently, this was extended to an elliptical shaped fiber with the same cross section area as the circular fiber. It was shown that the transverse composite thermal conductivity depends strongly on the fiber shape [2]. In this report, an expression is presented for a configuration with two circular fiber filaments in a unit cell of square packing array. The arrangement is shown as in Fig.1. One filament is located in the center of the cell and one quarter of the filament located at each of the four corners of the cell. Assuming that the radius of circular fiber is r , and the size of the unit cell is $4a^2$, since there are two filaments per cell, the volume fraction is

$$v_f = 2\pi r^2 / 4a^2 \quad (1)$$

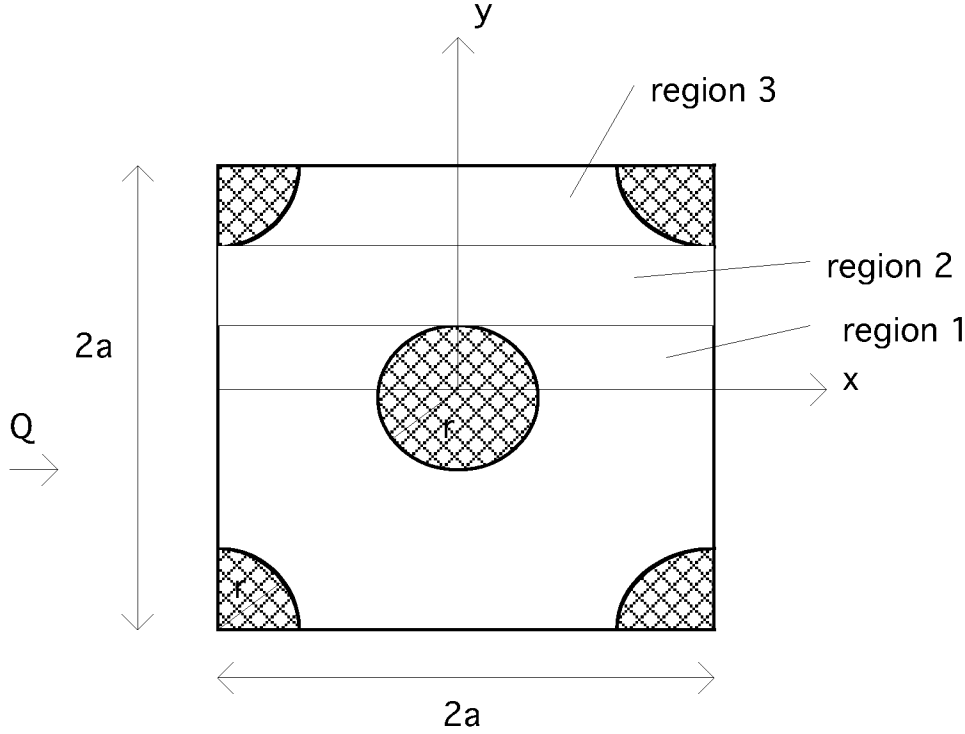


Fig . 1 Fundamental elements used in thermal modeling
for fiber radius $r \leq a/2$ arrangement

The heat flow is from the left to right and Fig. 1 is symmetrical with respect to reflection in both x and y directions. To obtain an expression for the thermal conductivity, it is only necessary to consider the heat flow in the upper half of the cell. The upper cell is further divided into three regions with limits in the y direction, from 0 to r, r to a-r and a-r to a respectively, while the limit in x is from -a to a for all regions. In region 2, there is only matrix; in regions 1 and 3, there is fiber as well as matrix. As far as the thermal model is concerned, the same amount of heat is conducted in region 1 and region 3, because regions 1 and 3 occupy the same area, and contain same shape of fiber. As the radius of fiber increases from 0 to $a/2$, region 2 decreases to 0, i.e., there is no direct passage for heat to traverse through the cell without intersecting the fiber. As r increases from $a/2$ to the maximum, $a/\sqrt{2}$ shown in Fig. 2, it is necessary to redefine the regions of interest. Region 1 is now redefined as $y=0$ to $y=a-r$; region 2 is redefined as $y=a-r$ to $y=r$; region 3 is redefined as $y=r$ to $y=a$. Following [1], the ratio of transverse thermal conductivity k_{22} to the matrix thermal conductivity k_m is written as

$$\begin{aligned}
k_{22} / k_m &= \left(1 - \frac{2r}{a}\right) + 2 \int_0^r \frac{dy}{a + x\left(1 - \frac{k_m}{k_f}\right)} \\
&= \left(1 - \frac{2r}{a}\right) + \frac{1}{B} \left[\pi - \frac{4}{\sqrt{1 - \frac{r^2 B^2}{a^2}}} \tan^{-1} \frac{1 - \frac{rB}{a}}{\sqrt{1 - \frac{r^2 B^2}{a^2}}} \right]
\end{aligned} \tag{2}$$

where k_f is the thermal conductivity of the fiber, $r \leq a/2$, and $r^2 B^2 / a^2 \leq 1$

$$B = \left(1 - \frac{k_m}{k_f}\right) \text{ and } x^2 + y^2 = r^2$$

However, the expression takes a different form when $r^2 B^2 / a^2 \geq 1$

$$k_{22} / k_m = \left(1 - \frac{2r}{a}\right) + \frac{1}{B} \left[\pi - \frac{2}{\sqrt{\frac{r^2 B^2}{a^2} - 1}} \log \left| \frac{B \frac{r}{a} - 1 + \sqrt{\frac{r^2 B^2}{a^2} - 1}}{B \frac{r}{a} - 1 - \sqrt{\frac{r^2 B^2}{a^2} - 1}} \right| \right] \tag{3}$$

Notice that B is defined differently than in Ref. [1]. As r increases beyond $a/2$, the ratio can be expressed as

$$k_{22} / k_m = 2 \int_0^{a-r} \frac{dy}{B\sqrt{r^2 - y^2} + a} + \int_{a-r}^r \frac{dy}{B(\sqrt{r^2 - y^2} + \sqrt{r^2 - (y-a)^2}) + a} \tag{4}$$

where $a/2 \leq r \leq a/\sqrt{2}$. Eq.(4) can be solved readily by numerical quadrature. Eqs.(2), (3) and (4) can be expressed in terms of volume fraction v_f by relation (1)

$$\begin{aligned}
k_{22} / k_m &= \left(1 - \sqrt{\frac{8v_f}{\pi}}\right) + \frac{1}{B} \left[\pi - \frac{4}{\sqrt{1 - \frac{2v_f B^2}{\pi}}} \tan^{-1} \frac{1 - B\sqrt{\frac{2v_f}{\pi}}}{\sqrt{1 - \frac{2v_f B^2}{\pi}}} \right] \\
\text{where } \sqrt{\frac{2v_f}{\pi}} &\leq \frac{1}{2}, \quad \frac{2v_f B^2}{\pi} \leq 1
\end{aligned} \tag{5}$$

and

$$k_{22} / k_m = (1 - \sqrt{\frac{8v_f}{\pi}}) + \frac{1}{B} \left[\pi - \frac{2}{\sqrt{\frac{2v_f B^2}{\pi} - 1}} \log \left| \frac{B\sqrt{\frac{2v_f}{\pi}} - 1 + \sqrt{\frac{2v_f B^2}{\pi} - 1}}{B\sqrt{\frac{2v_f}{\pi}} - 1 - \sqrt{\frac{2v_f B^2}{\pi} - 1}} \right| \right]$$

where $\sqrt{\frac{2v_f}{\pi}} \leq \frac{1}{2}$, $\frac{2v_f B^2}{\pi} \geq 1$ (6)

$$k_{22} / k_m = 2 \int_0^{1-\sqrt{\frac{2v_f}{\pi}}} \frac{dz}{B\sqrt{\frac{2v_f}{\pi} - z^2} + 1} + \int_{1-\sqrt{\frac{2v_f}{\pi}}}^{\sqrt{\frac{2v_f}{\pi}}} \frac{dz}{B[\sqrt{\frac{2v_f}{\pi} - z^2} + \sqrt{\frac{2v_f}{\pi} - (z-1)^2}] + 1}$$

where $\frac{1}{2} \leq \sqrt{\frac{2v_f}{\pi}} \leq \frac{1}{\sqrt{2}}$ (7)

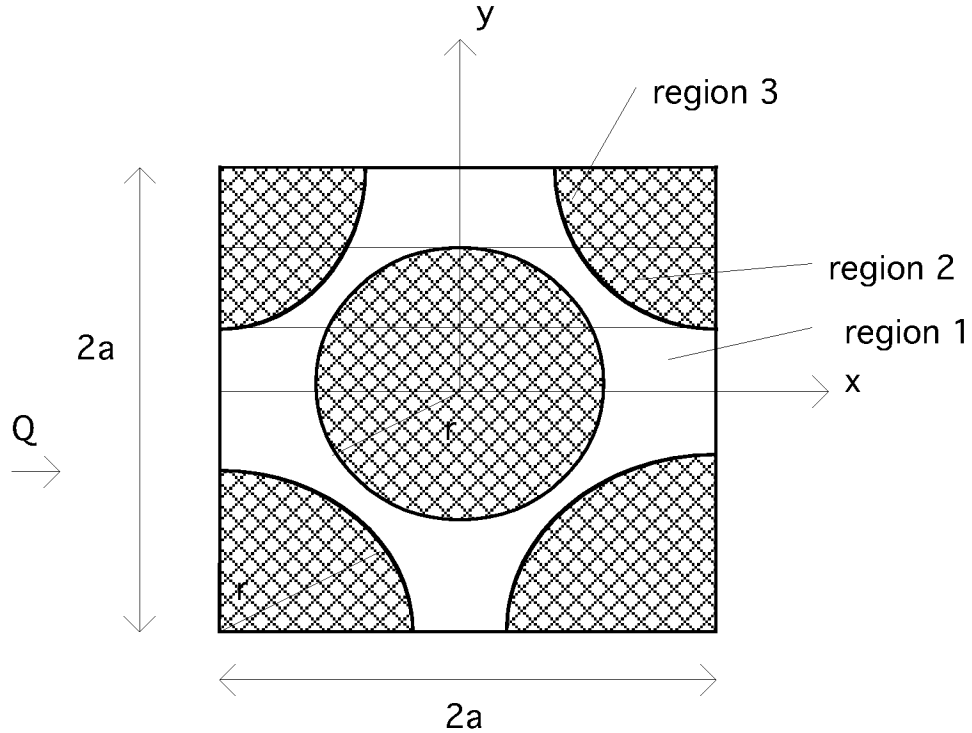


Fig . 2 Fundamental elements used in thermal modeling for fiber radius $r \geq a/2$ arrangement

II. Comparison of Results

In the following, Eqs. (5), (6) and (7) are used to compute the k_{22}/k_m ratio. These results are compared to results from reference [1] for the ratio determined as a function of fiber volume fraction v_f . Fig. 3 presents a comparison of the models and data for k_f/k_m equal to 666 and Fig. 4 presents results for k_f/k_m equal to 4.4 as was done in reference [1]. As expected, the 2 circular fibers per cell model predicts lower values for composite transverse conductivity than the single fiber models for the most of the range of v_f . The exception is for large k_f/k_m ratios and extremely high volume fraction where its value is higher than the value predicted by the single fiber square model, but lower than the single fiber circular cross section model. The lower values of two fiber model thermal conductivity can be explained in a qualitative sense; for the same v_f , the two fiber model has a more “serial” nature than the single fiber model, and therefore tends to predict a lower value. In an intuitive sense, introducing more fibers tends to further partition the matrix, so that the heat conduction suffers more impedance. On other hand, the two fiber model is a closer match to reality than the single fiber model because this arrangement allows the fibers to interlace together when the fiber radius increases beyond $a/2$, whereas the single fiber model definitely lacks of this characteristic. The experimental results of Thornburg and Pears [3] published in 1965, are shown by x’s in Fig. 3 and 4. These results seem to be in better agreement with the single fiber model when the k_f/k_m is high, but in better agreement with the two fiber model when k_f/k_m is low. Of course, this is by no means conclusive, and we think this comparison really opens a new issue. What is clear is the predicted equivalent transverse thermal conductivity for a given value of volume fraction of the filaments depends upon the adopted models as clearly demonstrated here. To verify which is the correct model for predicting composite conductivity, a few carefully controlled experiments are required to establish the data base and enhance our understanding of the transverse heat conduction phenomenon in composite. From those experiments and theoretical models, we can gain an improved understanding of the mechanisms of heat conduction in composites and how to best expand the existing models for transverse composite conduction.

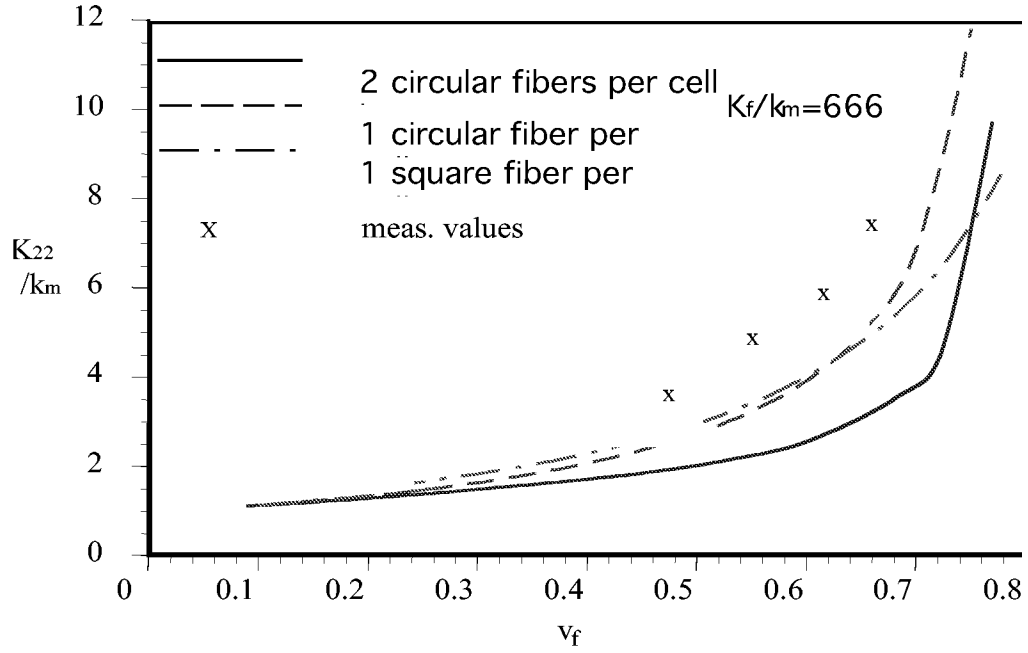


Fig. 3 Comparison of composite transverse thermal conductivity from different models for higher ratio of k_f/k_m .

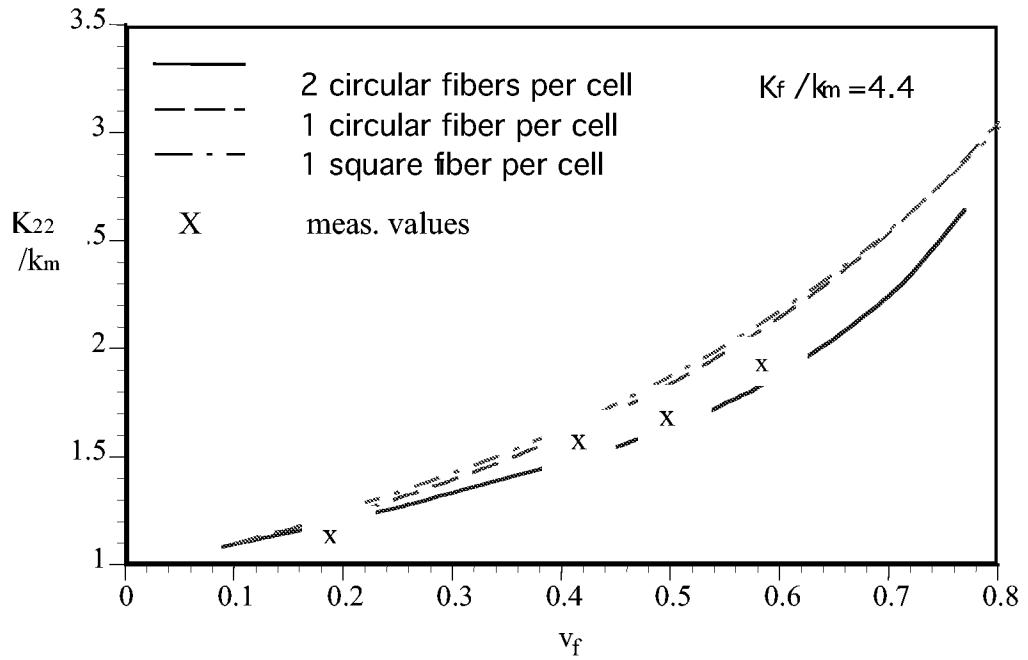


Fig. 4 Comparison of composite transverse thermal conductivity from different models for lower ratio of k_f/k_m .

Nomenclature

$2a, 2a$ = Fiber spacing in x and y direction

B = Dimensionless parameter , $B \equiv (\frac{k_m}{k_f} - 1)$

Q = average heat flux per unit cell length

v_f = volume fraction $= 2\pi r^2 / 4a^2$

k_{22} = composite thermal conductivity the direction normal to the fibers

k_m = thermal conductivity of matrix

k_f = thermal conductivity of fiber in the direction normal to the fibers

References

- [1] G. S. Springer and S. W. Tsai, "Thermal conductivities of unidirectional materials", J. Composite Materials, v.1, 166, 1967.
- [2] H. Tai, "Dependence of the transverse thermal conductivity of unidirectional composites on fiber shape", Int. J. Thermophysics, v.19, 5, p1485, 1998.
- [3] J. D. Thornburg and C. D. Pears, "Prediction of the thermal conductivity of filled and reinforced plastics", ASME Paper 65-WA/HT-4, 1965.

REPORT DOCUMENTATION PAGE			Form Approved OMB No. 0704-0188	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.				
1. AGENCY USE ONLY (Leave blank)	2. REPORT DATE May 2002	3. REPORT TYPE AND DATES COVERED Technical Memorandum		
4. TITLE AND SUBTITLE On the Thermal Model of Transverse Flow of Unidirectional Materials		5. FUNDING NUMBERS 706-61-11-01		
6. AUTHOR(S) Hsiang Tai				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) NASA Langley Research Center Hampton, VA 23681-2199		8. PERFORMING ORGANIZATION REPORT NUMBER L-18090		
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) National Aeronautics and Space Administration Washington, DC 20546-0001		10. SPONSORING/MONITORING AGENCY REPORT NUMBER NASA/TM-2002-211649		
11. SUPPLEMENTARY NOTES				
12a. DISTRIBUTION/AVAILABILITY STATEMENT Unclassified—Unlimited Subject Category 24 Distribution: Standard Availability: NASA CASI (301) 621-0390		12b. DISTRIBUTION CODE		
13. ABSTRACT (Maximum 200 words) The thermal model for transverse heat flow of having single filament in a unit cell is extended. In this model, we proposed that two circular filaments in a unit cell of square packing array and obtained the transverse thermal conductivity of an unidirectional material.				
14. SUBJECT TERMS Thermal model; Transverse flow; Unidirectional materials; Unit cell; Volume fractions			15. NUMBER OF PAGES 12	
			16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT Unclassified	18. SECURITY CLASSIFICATION OF THIS PAGE Unclassified	19. SECURITY CLASSIFICATION OF ABSTRACT Unclassified	20. LIMITATION OF ABSTRACT UL	